

Chapter 300

Bases - 24

This chapter is not part of the Project's specifications but is a guide for project personnel in interpreting CDOT specifications, understanding ASTM, AASHTO, and Colorado Procedures (CPs) for testing, and for completing CDOT forms.

The design and construction of a pavement structure may include one or more base courses. A base course is a layer of material below the wearing surface of a pavement. Bases may be constructed of gravels, mixtures of soil and aggregate, mixtures of asphalt and aggregate, mixtures of cement and aggregate or soil, or other innovative materials. Bases may be made of unbound materials, such as gravel, or bound materials, such as lime-treated subgrade.

Base courses under concrete pavements provide a drainage layer, reduce pumping, provide protection against frost damage, and provide support for the heavy equipment used for placing concrete pavements. There is some increase in structural capacity when a base is placed under a concrete pavement, but it is typically not a significant amount.

Base courses under flexible pavements provide a significant increase in structural capacity. The pavement design of flexible pavement depends on the wheel loads being distributed over a greater area as the depth of the pavement structure increases. There are the added benefits of improved drainage and protection against frost damage.

ITEM 206 STRUCTURE BACKFILL

ITEM 304 AGGREGATE BASE COURSE

Compaction of unbound bases is important for the stability of the pavement it supports. The maximum dry density is established in the laboratory before construction. During construction measurements of the base dry density are compared to the maximum dry density. The requirements for compaction of aggregate base course (ABC) are shown in Subsection 304.06 of the Standard Specifications for Road and Bridge Construction. Structure Backfill has similar requirements as shown in Subsection 206.03.

Two methods to determine the maximum dry density of soils are AASHTO T 99 and AASHTO T 180. AASHTO T 99 is similar to ASTM D 698 and is commonly referred to as the Proctor Test, as it was first proposed by R. R. Proctor in 1933. AASHTO T 99 uses a 5.5 lb. rammer dropped from 12 in. When a 4 in. mold is used, three layers are compacted with 25 blows on each layer. When a 6 in. mold is used, three layers are compacted with 56 blows on each layer. AASHTO T 99 results in a compactive effort of 12,400 ft-lbf/ft³. AASHTO T 180 is similar to ASTM D 1557 and is commonly referred to as the Modified Proctor Test. AASHTO T 180 uses a 10 lb. rammer dropped from 18 in. When a 4 in. mold is used, five layers are compacted with 25 blows on each layer. When a 6 in. mold is used, five layers are compacted with 56 blows on each layer. This results in a compactive effort of 56,000 ft-lbf/ft³. Comparing compactive efforts, AASHTO T 180 produces four and a half times the compactive effort than a sample receives compacted according to AASHTO T 99.

AASHTO T 99 is the appropriate standard for compaction of cohesive soils, particularly if there is the potential for swelling when saturated. AASHTO T 180 is appropriate for granular soils, such as aggregate base course and Structure Backfill, Class 1.

There are four methods of determining moisture-density relationships by AASHTO T 180:

- Method A uses a 4 in. mold and the fraction of the soil passing a No. 4 sieve. AASHTO states that this is applicable to soil mixtures that have 40% or less retained on a No. 4 sieve.
- Method B uses a 6 in. mold and the fraction of the soil passing a No. 4 sieve. AASHTO states that this is applicable to soil mixtures that have 40% or less retained on a No. 4 sieve.
- Method C uses a 4 in. mold and the fraction of the soil passing a 3/4 in. sieve. AASHTO states that this is applicable to soil mixtures that have 30% or less retained on a 3/4 in. sieve.
- Method D uses a 6 in. mold and the fraction of the soil passing a 3/4 in. sieve. AASHTO states that this is applicable to soil mixtures that have 30% or less retained on a 3/4 in. sieve.

The Gradation requirements for Class 1 Structure Backfill and ABC are shown in Subsections 703.08 and 703.03 respectively. A review of the Gradation requirements shows that many granular materials will meet the Gradation requirements and exceed the limits of application stated in AASHTO T 180.

Colorado has developed a rock correction formula in Colorado Procedure 23 (CP 23) when AASHTO T 180 is used:

$$MDD_c = (P_f \times D_f) + (P_c \times 0.95 \times D_c) / 100$$

The standard practice within the Department follows:

- 110 lbs. of granular material are sampled and sent to the laboratory before construction begins. This would typically require two standard sample bags.
- The material is separated into two fractions, material retained on a No. 4 sieve and material passing a No. 4 sieve.
- The specific gravity and absorption of the material retained on a No. 4 sieve is determined according to AASHTO T 85 Specific Gravity and Absorption of Coarse Aggregate.
- The maximum dry density and optimum moisture of the material passing a No. 4 sieve is determined according to AASHTO T 180, Method A.
- For bases with crushed concrete or reclaimed asphalt pavement (RAP), an accurate specific gravity determination is difficult to make. For these materials T 180, Method D is used.
- Method D may be used if more than 30% of the material is retained on the No. 4 sieve, but has 30% or less of the material retained on the 3/4 inch sieve. When Method D is used, use the above procedure but substitute the 3/4 inch sieve for the No. 4 sieve.

During construction, the control of compaction follows according to the plans, specifications, and the Frequency Guide Schedule for Minimum Materials Sampling, Testing, and Inspection. Each field test must include a separation of the sample into the two fractions, material retained on a No. 4 sieve, and material passing a No. 4 sieve. Percent relative compaction is determined according to CP 25. CP 23 is used to correct the maximum dry density and optimum moisture for soil-rock mixtures with more than 5% material retained on a No. 4 sieve.

ITEM 308 PORTLAND CEMENT & FLY ASH

Sources of Portland cement and/or fly ash are listed on the Department's Approved Product List. To verify a specific cementitious material that may be considered for a project check if the supplier/manufacturer of the cement or fly ash is on the Approved Products List at the web site address of: <https://www.codot.gov/business/apl>

If a manufacturer wants to add a cement or fly ash source use the same website and follow the instructions within Notice to Manufacturers: <https://www.codot.gov/business/apl/manufacturers.html> and also follow all references within CP 11:

CDOT Materials Forms – Follow the link provided to access the applicable forms for Bases

<https://www.codot.gov/library/forms/form-numbers-broken-down>

Form	Title
157	Field Report for Sample Identification or Materials Documentation
6	Field Tests of Base Aggregate, Fillers, Paving and Miscellaneous Aggregates
38	Aggregate Test Report - [<i>computer output</i>] SiteManager
194	Structure Backfill Density Report
564	Soils and Aggregate Sieve Analysis When Splitting On the No. 4 Sieve
565	Sieve Analysis For Aggregate Not Split On the No. 4 Sieve
633	Sample Tag (Sacks)
1126	Stabilometer Record of Item 304 Aggregate Base Course
1296	Granular Materials Moisture – Density Report - [<i>computer output</i>] SiteManager

CDOT Form 167

COLORADO DEPARTMENT OF TRANSPORTATION FIELD REPORT FOR SAMPLE IDENTIFICATION OR MATERIALS DOCUMENTATION			FS# = (Contract ID-Seq.#)			
			Region	_____		
			Contract ID	Date Submitted		
			Project No.	_____		
Project Location			_____			
Material Type		Field Lab phone		Cell Phone		
Material Code (LIMS)	Item	Class	Grading	Special Provisions <input type="checkbox"/> yes		
Previously used on Project No.:		Previous CDOT Form #157 F/S No.(s):		<input type="checkbox"/> CDOT Form #633 (sack) <input type="checkbox"/> CDOT Form #634 (can)		
● Sample Identification: Quantity & Unit of material submitted, describe tests required, precise location sample remove from (Stationing), etc. ● Materials Documentation: Field inspected (describe appearance, weight/dimensions, model/serial number), COC &/or CTR provided etc.						
Central Lab use only:						
Sample ID (#1)		Sample ID (#2)		Sample ID (#3)		
Sample ID (#4)		Sample ID (#5)		Sample ID (#6)		
APL/QML Acceptance: APL Ref. No.		Product name:		Date checked:		
APL/QML Acceptance: APL Ref. No.		Product name:		Date checked:		
Preliminary <input type="checkbox"/>		Construction <input type="checkbox"/>		Date needed		
Maintenance <input type="checkbox"/>		Emergency <input type="checkbox"/>				
Contractor			Supplier			
Sampled from <small>(Pit, roadway, windrow, stock, etc.)</small>			Pit name or owner			
Quantity represented		Previous quantity		Total quantity to date		
Sample submitted: <input type="checkbox"/> Yes <input type="checkbox"/> No		Shipped specified quantity to: <input type="checkbox"/> Central lab <input type="checkbox"/> Region lab <input type="checkbox"/> Consultant lab		Date		
Sampled or inspected by (print name)		Title		E-mail		
Supervisor (Pro./Res./Mats. Engr./Maint. Supt.) (print name)		Title		Residency		

Distribution: Chemical Lab: cdot_chemlab@state.co.us
 Concrete Lab: cdot_conc.lab@state.co.us
 Flexible Pavement: cdot_flex.lab@state.co.us
 Physical Properties: cdot_phpr.lab@state.co.us
 Soils Lab: cdot_soils.lab@state.co.us
 Region Labs: Send completed form with sample

Previous editions are obsolete and may not be used. CDOT Form #167 04/18
 Project File: SMM – Upload completed form into the attachment icon on the sample record

CDOT Form 194

COLORADO DEPARTMENT OF TRANSPORTATION STRUCTURE BACKFILL DENSITY REPORT	Region	Date Submitted
	Contract ID	
	Project No.	
	Project Location	

Major Structures

Number of Structures: (1 test/200 cu. yds.; minimum 1/structure)	Class 1 (cu. yds.)	No. of tests	Class 2 (cu. yds.)	No. of tests
Total cu. yds. structure backfill:				

Cross Drains


Number of Cross Drains: (1 test/200 cu. yds.; minimum 1/structure)	Class 1 (cu. yds.)	No. of tests	Class 2 (cu. yds.)	No. of tests
Total cu. yds. structure backfill:				

Side Drains

Number of Side Drains: (1 test/200 cu. yds.; minimum 1/structure)	Class 1 (cu. yds.)	No. of tests	Class 2 (cu. yds.)	No. of tests
Total cu. yds. structure backfill:				

Other

	Class 1 (cu. yds.)	No. of tests	Class 2 (cu. yds.)	No. of tests

Remarks		
Print name	Signed 	Title

CDOT Form 564 Page 1

COLORADO DEPARTMENT OF TRANSPORTATION					Contract No.	Region	Date
Soils & AGGREGATE SIEVE ANALYSIS WHEN SPLITTING ON THE No. 4 SIEVE					Project No.		
CP 21, CP 31 / AASHTO T89, T90, M146 / CPL-2104					Project Location		
Soil Description					PIE Name		
Pilot Location					NOTE: Do not use this form when NOT splitting over the #4 Sieve. Use CDOT Form 565.		
Sample ID SMM		Lab Reference Number SMM			Pan		
Total (+ #4) Gradation					Total No.		
Total Moist Sample Weight		Total (+ #4) Moist Sample Weight		Total (- #4) Dry Sample Weight	Tested by		
Sieve	Weight	Percent Retained	Percent Passing	Specs	Sample Information		
4"					Sampled From		
3"					Supplier Ticket No.		
2 1/2"					Time Sampled		
2"					Station		
1 1/2"					Lane		
1"					Quantity Sample Represents		
3/4"					(- #4) % Moisture and Dry Weight		
1/2"					Pan ID		
3/8"					Pan Weight		
(+ #4)					Pan & Sample - Wet Weight (g)		
Total (- #4) Moist Wt.					Pan & Sample - Dry Weight (g)		
<p>CP 21 Section 6.2: Calculate the percent passing for the #8 - #200 by multiplying the percent passing each sieve of the washed sieve analysis specimen by the percent passing the (+ #4) sieve of the total sample divided by 100.</p>					Sample - Wet Weight (g)		
					Sample - Dry Weight (g)		
					Moisture Loss (g)		
					Moisture Content (MC) %		
					Specimen Dry Weight (SDW_1)		
(- #4) Gradation Washed Sieve Analysis					If a separate (- #4) moisture sample is used to determine dry mass of gradation sample, use calculation below to determine (- #4) Sample Dry weight before wash (SDW_2) using the MC above.		
(- #4) Sample Dry weight before wash (SDW_1 or _2)		(- #4) Dry weight after wash (DWW)					
Sieve	Weight	Percent Retained	Percent Passing Washed Sieve		(- #4) Wet Weight + (100 + MC %) x 100 = (-#4) Sample Dry Wt(SDW_2) (- #4) Wet WT. _____ + (100 + _____) x 100 = _____ SDW_2 IA Sample ID Place IA Stamp Here Electronic Signature of IA Personnel		
#8							
#10 - Soils							
#16							
#30							
#40 - Soils							
#50							
#100							
#200							
- #200 TSW					Electronic Signature of IA Personnel		
(DWW - TSW) ÷ DWW x 100 = % Diff (Spec: ≤ 0.3%) _____ ÷ _____ x 100 = _____ %							
Comments							

CDOT Form 564 Page 2

ATTERBERG LIMIT WORK SHEET					
Tested by:		Contract ID:		Sample ID:	
LIQUID LIMIT			Number of Blows	Multiplier	
TIN ID			22	0.9850	
A = Mass of Tin			23	0.9900	
B = Mass of Tin + Wet Soil (g)			24	0.9950	
C = Mass of Tin + Dry Soil (g)			25	1.0000	
D = Wt of wet soil (B-A) (g)			26	1.0050	
E = Wt of dry soil (C-A) (g)			27	1.0090	
F = LOSS (D-E) (g)			28	1.0140	
Moisture Content = (F + E) x 100			LL% = Moisture Content @ number of blows X Multiplier.		
Number of Blows					
Liquid Limit (%)			Plastic Index		Specifications
PLASTIC LIMIT			Liquid Limit %		
Tin ID			Plastic Limit %		
A = Mass of Tin			Plasticity Index		
B = Mass of Tin + Wet Soil (g)			M145 Soil Classification		
C = Mass of Tin + Dry Soil (g)			#10		
D = Wt of wet soil (B-A) (g)			#40		
E = Wt of dry soil (C-A) (g)			#200		
F = LOSS (D-E) (g)			AASHTO Classification		▼
Moisture Content = (F + E) x 100					

WATER SOLUBLE SULFATES WORK SHEET			
Sample ID:	Date Received:	Test date:	Project No.:
Sample location:			
Soil Description:			
Tested by (print name):		A) Number of dilutions: _____ = y	
Sample date:		B) Final dilution (10 Y: 1)	
Sample bottle ID:		C) Reading: _____	
Saturation date:		D) Corrected reading _____	
Saturation time:		E) Sulfate concentration _____	
Test start time:		E = (B x D) (<input type="radio"/> mg/L <input type="radio"/> ppm <input type="radio"/> %)	

Simplified Procedure


- | | |
|---|---|
| <ol style="list-style-type: none"> 1) Dry soil (<140° F/60° C) and process through the #4 sieve. 2) Process a representative sample through a #40 sieve. 3) Place a 25g representative sample into clean flask or container. 4) Add 250ml distilled water and shake well. (10:1 dilution). 5) Let stand undisturbed for a minimum of 16 hrs maintaining the solution @ 140° F (+/- 5° F). 6) Pipet 25ml of standing solution and deposit into clean 500ml flask (do not disturb sediment). If sample exhibits turbidity then filter until clear. 7) Dilute test sample to 250ml by adding 225ml of distilled water. (100:1 dilution). | <ol style="list-style-type: none"> 8) Pipet 10ml of sample into sample cells (1 blank, 1 reaction sample). 9) Add reagent to 1 cell, shake well and let stand a minimum of 5 min. and not more than 10 min. 10) Place blank into colorimeter and zero the meter. 11) Replace blank with reacted sample and take reading. 12) Record the reading. (mg/L to 10, ppm to 10, % to 0.01). 13) If the reading exceeds the limits of the meter discard test sample and blank. Clean the sample cells. Dilute sample further by taking 25ml from the 10:1 test sample (step 4) and dilute to 500ml. (200:1 dilution) Repeat steps 8 - 12. Continue dilutions until a reading is obtained. |
|---|---|

CDOT Form 565


Colorado Department of Transportation Sieve Analysis for Aggregates CP31 Atterberg Limits T89 and T90					Contract ID:	Region:
Material Description:					Project Number:	
Prime Contractor:					Project Location:	
Sample ID SMM:					Class:	Test No:
Lab Ref Number SMM:					Test Date:	
Do not use this form for Item 200 - Soils or Item 206 - Structure Backfill Class 2; use Form 564 split over the 84 - CP 21.						
Gradation Specimen Dry Weight (SDW):			Washed Dry Weight (WDW):		Sample Information	
Sieve	Weight	Percent Retained	Percent Passing	Specs		
5"					Sampled From:	
4"					Supplier Ticket No:	
3"					Time Sampled:	
2 1/4"					Station:	
2"					Lane:	
1 1/2"					Quantity Sample Represents:	
1"					Sampling witnessed by:	
3/4"					Sample Tested By:	
5/8"					Sample % Moisture and Dry Weight	
3/8"					Pan ID:	
3/16"					Pan Weight (g): A	
1/4"					Pan & Sample - Wet Weight (g): B	
#4					Pan & Sample - Dry Weight (g): C	
#8					Sample - Wet Weight (g): D=(B-A)	
#16					Sample - Dry Weight (g): E=(C-A)	
#30					Moisture Loss (g): F=(D-E)	
#50					Moisture Content (MC) %: G=(F/E) x 100	
#100					Specimen Dry Weight: E	
#200					If gradation sample and moisture sample are the same sample, use the dry weight (SDW) in the sieve analysis calculations.	
- #200		(WDW - TSW) ÷ WDW x 100 = % Diff (Spec: ≤ 0.3%)			Gradation Remarks:	
Total Sieved WT (TSW):		() ÷ () x 100 = %				
Wet Weight ÷ (100 + MC %) x 100 = Specimen Dry Weight					If a split moisture sample is used to determine dry mass of gradation sample, use calculation to determine dry weight.	
Wet WT. ÷ (100 +) x 100 = SDW						
Atterberg Limits:		Liquid Limit T89	Plastic Limit T90		Place IA Stamp Here:	
Tin ID:						
Mass of Tin:						
Mass of Tin + Wet Soil:						
Mass of Tin + Dry Soil:			Number of Blows	Multiplier	IA Sample ID:	
Moisture Content %:			22	0.9850	Electronic Signature of IA Personnel	
Number of Blows:			23	0.9900	Sample Remarks:	
Plasticity Index:		Specifications	24	0.9950		
Liquid Limit %:			25	1.0000		
Plastic Limit %:			26	1.0050		
Plasticity Index:			27	1.0090		
LL % = Moisture Content @ number of blows X multiplier			28	1.0140		

Previous editions are obsolete and may not be used.

CDOT Form 633 (Tag)

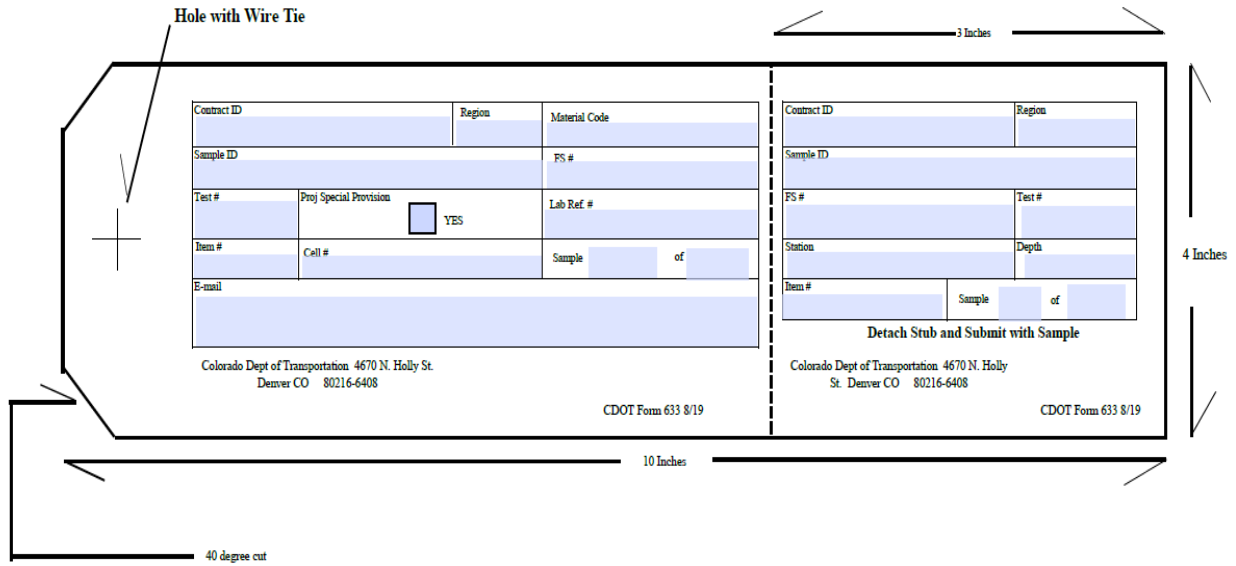

CDOT Form 633 Tag (w/preforated tag and wire tie)

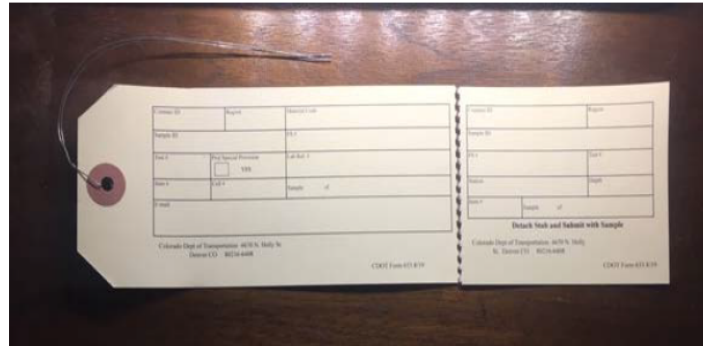

CDOT Form 157

COLORADO DEPARTMENT OF TRANSPORTATION FIELD REPORT FOR SAMPLE IDENTIFICATION OR MATERIALS DOCUMENTATION				FIS# = (Contract ID-Seq.#)	
				Region	
				Contract ID	Date Submitted
				Project No.	
Project Location					
Material Type			Field Lab phone		Cell Phone
Material Code (LIMS)	Item	Class	Grading	Special Provisions <input type="checkbox"/> YES	
Previously used on Project No.:		Previous CDOT Form 157 FIS No.(s):		<input type="checkbox"/> CDOT Form #633 (asph) <input type="checkbox"/> CDOT Form #634 (con)	
<p style="color: red; font-size: small;"> • Sample Identification: Quantity & Unit of material submitted, describe tests required, precise location sample remove from (Stationing), etc. • Materials Documentation: Field Inspected (describe appearance, weight/dimensions, model/serial number), COC &/or CTR provided etc. </p>					
Central Lab use only:					
Sample ID (#1)		Sample ID (#2)		Sample ID (#3)	
Sample ID (#4)		Sample ID (#5)		Sample ID (#6)	
AP/DQML Acceptance: APL Ref. No.		Product name:			Date checked:
AP/DQML Acceptance: APL Ref. No.		Product name:			Date checked:
Preliminary <input type="checkbox"/>		Construction <input type="checkbox"/>		Maintenance <input type="checkbox"/>	
Emergency <input type="checkbox"/>		Date needed			
Contractor			Supplier		
Sampled from <small>(Pit, roadway, windrow, stock, etc.)</small>			Pit name or owner		
Quantity represented		Previous quantity		Total quantity to date	
Sample submitted:	Shipped specified quantity to:				Date
<input type="checkbox"/> Yes <input checked="" type="checkbox"/> No	<input type="checkbox"/> Central lab	<input type="checkbox"/> Region lab	<input type="checkbox"/> Consultant lab		
Sampled or inspected by (print name)		Title		E-mail	
Supervisor (Print/Full Name, Ingt/Ident. Sup.) (print name)		Title		Residency	

Distribution: Chemical Lab: cdot_chemlab@state.co.us
 Concrete Lab: cdot_conc_labs@state.co.us
 Soils Lab: cdot_soils_labs@state.co.us

Physical Properties: cdot_phyr_lab@state.co.us
 Flexible Pavement: cdot_flex_lab@state.co.us

CDOT Form 157 04/2022

Previous editions are obsolete and may not be used.